

LARGE EDDY SIMULATIONS OF TURBULENT FLOW AND INCLUSION TRANSPORT IN CONTINUOUS CASTING OF STEEL

Quan Yuan, S. P. Vanka and Brian G. Thomas

Department of Mechanical and Industrial Engineering

University of Illinois at Urbana-Champaign

1206 W Green Street, Urbana, IL 61801 USA

quanyuan@uiuc.edu, s-vanka@uiuc.edu, bgthomas@uiuc.edu

ABSTRACT

Turbulent structures are important in influencing inclusion transport in continuous casting of steel. The turbulent velocity field and inclusion transport are studied in a full-scale water model using large eddy simulations. The computed fluid velocities are compared with measurements. Chaotic vortex structures were computed in the upper roll region as expected. The computed inclusion trajectories were processed to determine the inclusion removal rate to the top surface. The results agree reasonably with measurements from the water model. The removal of particle inclusions to the top surface is found to be independent of the particle initial positions at which they enter the mold.

INTRODUCTION

Turbulence plays an important role in continuous casting of steel. The transient turbulent structures in the mold region of a continuous caster influence the entrapment of the top surface flux layer and the motion of inclusion particles. The inclusions exiting the submerged entry nozzle (SEN) may either float to the top surface and get safely removed into the slag layer, or may be trapped in the solidifying front, leading to defects such as internal cracks and slivers in the final rolled product.

A number of previous studies have analyzed this flow using Reynolds-averaged turbulence models, typically the $k-\epsilon$ model. However, the $k-\epsilon$ model gives only the time-averaged transport, and at best only crudely predicts the turbulence dynamics and particle transport by turbulence.

Large Eddy Simulations (LES) of turbulence provide an attractive method for simulating turbulent flows. In comparison with the Reynolds-averaged approach, LES provides much more realistic and accurate representation of a turbulent flow by resolving the large-scale dynamics. This information is crucial in estimating the heat mass and momentum transport, and transport of inclusions. Turbulence is also important in estimating the entrapment of the flux layer on the top surface of the mold. LES has been applied in the past to model many simple turbulent flows. However, its application to a highly complex flow such as that in the mold region of a continuous caster presents many new challenges. These

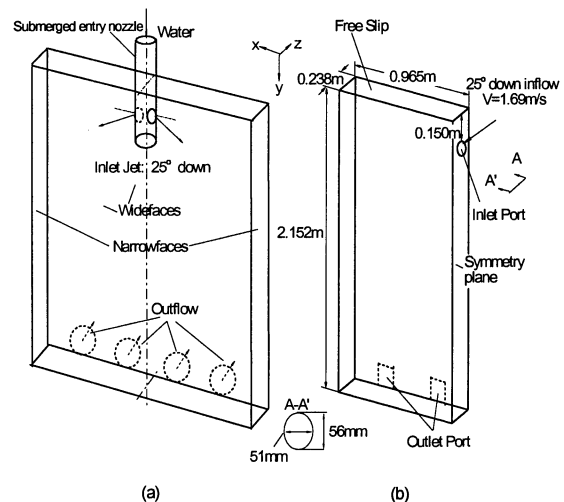


Figure 1: Schematic of (a) water model and (b) simulation domain.

include prescription of the correct inlet conditions to the computational domain, adequately resolving all velocity and thermal boundary layers, simulating the two-phase flow resulting from injection of argon bubbles and inclusions, and resolving the transient solidification front. Further, experiments in water models have shown the presence of large-scale unsteadiness in the flow, which mandates long simulation times. Therefore, the computational burden of such simulations is very high.

Because of nearly equal kinematic viscosities of the liquid steel and water which determine the main flow characteristics, flow in the steel caster mold region can be studied using scaled water models. In the present study, we have conducted LES of the flow in a full-scale water model. Our objective is to understand the instantaneous structures in the flow and the motion of inclusion particles, and to compare the LES results with experimental data where available.

PROBLEM DESCRIPTION

Figure 1 shows an experimental set-up at AK Steel Company (Sussman, 1992), and the corresponding computational domain used to simulate this water model experiment. In the experiment, around 8000-30000 elliptical disk-shaped plastic beads were injected into the mold

with the water through the nozzle to study the particle transport. The density and size of the beads were chosen to match the vertical terminal velocity of 300 μ m alumina inclusions in the liquid steel. A screen was positioned near the top surface to trap the plastic beads and thereby simulate the fraction of inclusion particles removed to the top surface. The experiments were repeated for at least five times and the averaged inclusion removal by the screen was reported (Sussman, 1992). A hot-wire anemometer was used to measure the fluid velocity field.

The LES was conducted to study the flow and particle transport for this water model to compare with the experiments and gain more insights. At the inlet, the instantaneous velocity profiles from a fully developed turbulent flow in a pipe are prescribed. The velocities are directed at an angle of 25° downwards to the horizontal axis. Only half of the mold domain is computed at this time with the assumption of symmetry about the central plane. The computational conditions are compared with those of the experiment in Table 1. Six groups of particles were introduced from the inlet within a short time period at different times, as shown in Table 2.

MATHEMATICAL MODELING

Fluid Flow

The time-dependent three-dimensional Navier-Stokes equations have been solved for the fluid velocity field. The Smagorinsky eddy viscosity model (Smagorinsky, 1963) is used to represent the unresolved scales:

$$\frac{\partial v_i}{\partial x_i} = 0 \quad (1)$$

$$\frac{Dv_i}{Dt} = -\frac{1}{\rho} \frac{\partial p}{\partial x_i} + \frac{\partial}{\partial x_j} v_{eff} \left(\frac{\partial v_i}{\partial x_j} + \frac{\partial v_j}{\partial x_i} \right) \quad (2)$$

$$v_{eff} = v_0 + 0.01(\Delta x \Delta y \Delta z)^{2/3} \sqrt{\frac{\partial v_i}{\partial x_j} \frac{\partial v_i}{\partial x_j} + \frac{\partial v_i}{\partial x_j} \frac{\partial v_j}{\partial x_i}} \quad (3)$$

The equations are discretized using the Harlow-Welch fraction step procedure (Robichaux, 1990) on a staggered grid. Second order central differencing is used for the convection terms and the Crank-Nicolson scheme is used for the diffusion terms. The Adams-Bashforth scheme is used to discretize in time with second order accuracy. The implicit diffusion terms are solved using Alternative Line Inversion. The pressure Poisson equation is solved using a direct Fast Fourier Transform solver. For parallelization, 1-D domain decomposition with MPI (Message Passing Interface) is utilized. The computation was conducted with a mesh consisting of 128×169×64 nodes in the x, y and z directions respectively. The time-dependent equations were integrated for 175,000 time steps (140 seconds of real time).

	Experiment	LES simulation
Nozzle port size /Inlet port size (x × y) (m)	0.051 × 0.056	0.051 × 0.056
Submergence depth (m)	0.150	0.150
Nozzle angle	25°	25°
Inlet jet angle	25°	25°
Mold /Domain height (m)	2.152	2.152
Mold /Domain width (m)	1.83	0.965
Mold /Domain thickness (m)	0.238	0.238
Average inlet flow rate (m ³ /s)	0.00344	0.00344
Average inlet speed (m/s)	1.69	1.69
Fluid density (kg/m ³)	1000	1000
Casting speed (m/s)	0.0152	0.0152
Fluid kinematic viscosity (m ² /s)	1.0×10 ⁻⁶	1.0×10 ⁻⁶
Particle inclusion size (mm)	2 – 3	3.8 (diameter)
Particle inclusion density (kg/m ³)	988	988
Corresponding alumina inclusion diameter in steel caster (μm)	300	300

Table 1: Experimental and simulation parameters.

Group index	Number of particles	Time of introduction
0	15000	0s – 1.6s
1	500	2s – 2.4s
2	500	4s – 4.4s
3	500	6s – 6.4s
4	500	8s – 8.4s
5	500	10s – 10.4s

Table 2: Particle injection data.

This computation takes 19.2 CPUs per time step on a Pentium III 750MHz PC or 39 days for 175,000 time steps.

Particle Transport

The Lagrangian approach is employed for particle transport. The particle equation of motion is:

$$v_{p,i} = \frac{dx_{p,i}}{dt} \quad (4)$$

$$\frac{dv_{p,i}}{dt} = \frac{18\rho v_0}{\rho_p d_p^2} (1 + 0.15 \text{Re}_p^{0.687}) (v_i - v_{p,i}) + (1 - \frac{\rho}{\rho_p}) g_i \quad (5)$$

where: $Re_p = \frac{|\bar{v}_p - \bar{v}| d_p}{\nu_0}$ (6)

The equations are integrated for each particle using a fourth order Runge-Kutta method at the same time as the velocity field is computed. This computation takes 2.4 additional CPUs per time step for 17500 particles or 5 additional days for 175000 time steps.

RESULTS AND DISCUSSION

Fluid Flow

Figure 2 shows a typical instantaneous velocity vector plot computed using LES. The flow emerges from the inlet port as a jet, diffuses as it traverses across the mold, impinges on the narrow face and splits into two recirculation regions consisting of the upper and lower rolls. This turbulent flow pattern is consistent with the experimental observations (Sussman, 1992; Thomas, 1994).

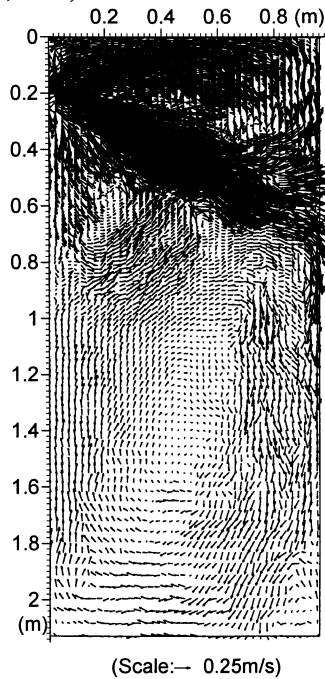


Figure 2: Computed typical instantaneous velocity field between wide faces.

Figures 3(a) and (b) show two typical instantaneous flow patterns of the upper roll. It is seen that the upper roll consists of a single large recirculation structure in Figure 3(a), but many distinct vortex structures in Figure 3(b). The upper roll alternates chaotically between these two extremes. This finding is consistent with a previous LES conducted for a 0.4-scale water model (Sivaramakrishnan, 2000). Only at the places very close to the top surface is the fluid velocity always horizontal. This finding is important in understanding the accuracy of the

indirect measurement of the liquid steel velocity in caster mold using electromagnetic sensors.

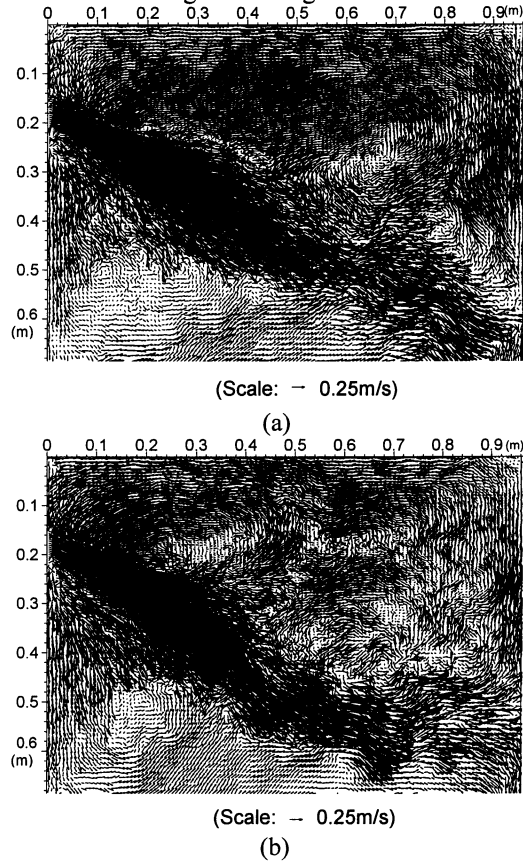


Figure 3: Instantaneous flow patterns in the upper roll.

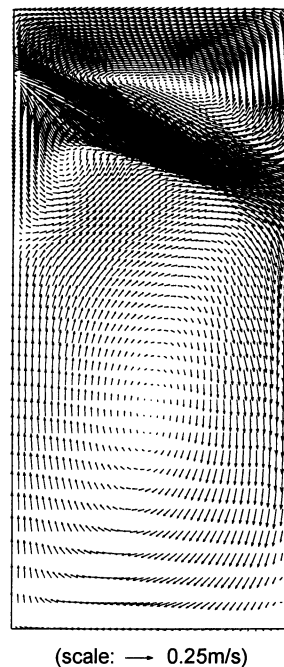


Figure 4: Time-averaged velocity field at the plane between wide faces.